

Intrinsic tunnelling or wishful thinking?

Heating is known to distort I-V linearity in superconductors, cf. eg. [1]. However, heating issues in ‘intrinsic tunnelling’ (IJT) were mostly misinterpreted or ignored until direct experimental evidence of the heating origin of I-V nonlinearities in Bi2212 mesas was obtained [2]. Subsequently the origin of IJT and some principal applications of the effect were addressed by [3] following the development of a practical tool for the distinction of intrinsic features from extrinsic ones and evidence of the heating origin of the key IJT findings including various IJT ‘gaps’ [4]. Krasnov et al [5] ignored earlier experimental work by Refs.[1, 2, 3] and in undeclared polemics with Ref.[3] claimed their I-V are free of heating because the sample area dependence of these I-V appears to be at odds with the model by [5]. This model, however, is irrelevant since it disregards convection and ignores the top-most *metal* electrode of the enhanced area and thermal conductivity, which is a principal heat-sinking channel in the mesas by [5]. As will be shown below, the ‘heat-free’ I-Vs by [5] are most probably caused by heating.

Heat load $P \equiv VI/A$ characterizes self-heating since the heat VI dissipated inside the sample escapes through its surface area A . Similarly to Refs.[3,4-6] in [5], the characteristic loads that are required to achieve the features in IJT spectra ascribed by [5] to different phenomena exceed that of a domestic kettle by 2-3 orders and are practically independent of A , hence pointing to the heating origin of these features, see Fig.1(a).

Mean overheating of a mesa-structure is described by Newton’s law of cooling (1701) as

$$T - T_B \propto P. \quad (1)$$

According to Eq.(1), monitoring I-V at a given bath temperature T_B results in a sample temperature rise that entails gap-like non-linearity if $\partial R/\partial T < 0$, Fig.1(b). Unlike the model by [5] the parameter-free Eq.(1) describes the measured IJT spectra *quantitatively* based on the $R(T)$ of the *same sample only* [3, 4]. Here we extend the analysis by [3, 4] to verify whether the independence of the IJT gap from the sample area *guarantees* the absence of self-heating as claimed by [5]. Assuming the samples differ by the area *only*, we reconstructed the IJT spectra for the same range of A using the model $R(T)$ by [5] reproduced in Fig.1(c). As seen from Fig.1(b), the thus constructed heating spectra reproduce all key findings by [5]. Indeed, irrespective of the mesa area, these spectra retain the same V-shape and slope below and above the IJT gap and even reveal some minor features ascribed by [5] to phonons. Hence the principal claim by Krasnov et al is revealed to be invalid and the area independence of the shape of the IJT spectra by [5] shows that the latter

indeed represent artefacts of self-heating.

It is worth noting that Eq.(1) explains naturally the *actual* area ‘dependences’ of IJT gaps by [5] that are *not flat*. Indeed, a direct estimate, $1/R = \partial I/\partial V|_{V \rightarrow 0}$, shows that the samples by [5] reveal vastly different *resistivities* in stark contrast to what would be expected if these were

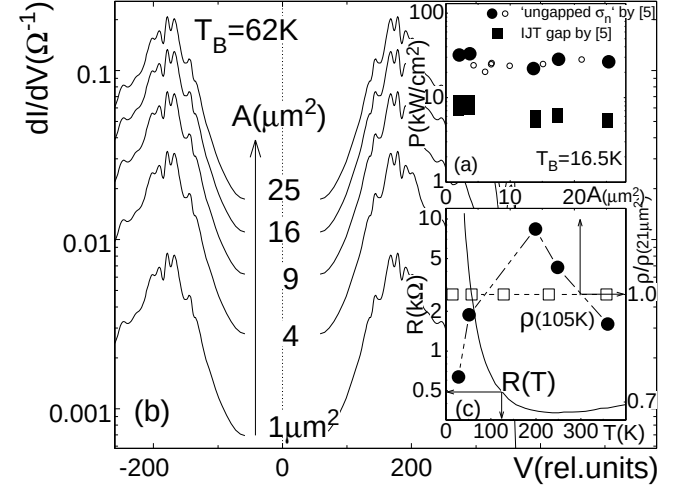


FIG. 1: (a): Heat loads that are required to achieve the characteristic IJT features by [5]; (b): $\partial I/\partial V$ for mesas of different area made of the same medium, obtained from the model $R(T)$ of [5] (solid line in (c)) assuming Joule heating origin of I-V nonlinearities; (c) the squares and circles represent $\rho(A)$ of physically identical media and those by [5] respectively.

physically identical, as is erroneously claimed by [5] and assumed in our calculations (see the symbols in Fig.1(c)). Hence Fig.2 by [5] becomes trivial as the IJT gaps of samples with different $\rho(T)$ should not necessarily match [4].

To save space, I will only briefly point to some other key faults by [5] that are carried over from earlier works and were already addressed by [3, 4]. In particular, the IJT spectra at $T_B < T_c$ are described by the same Eq.(1) that explains naturally the abnormal sharpness of the gap-like feature at $T_B/T_c \sim 0.03$, see [3] for details and also for the cause of I-V’s back-bending that has little in common with heating above T^* . Finally, the nonequilibrium thermometry by [5] is unreliable as it ignores the heat load dependent thermal lag, see [3, 4] for details.

In summary, our comprehensive analysis suggests the heating origin of key findings by [5], hence rendering irrelevant their conclusions.

V.N. Zavaritsky

Department of Physics, Loughborough University, UK;
Kapitza Institute and General Physics Institute, Moscow

[1] A.V.Gurevich, R.G. Mints, Rev.Mod.Phys **59**, 941 (1987).
[2] V.N.Zavaritsky, J Supercond. **15**, 567 (2002).

[3] see V.N.Zavaritsky, cond-mat/0410069 and Phys. Rev. B **72**, 094503 (2005) for more details.

- [4] V.N. Zavaritsky, cond-mat/0306081; see also Physica C**404**, 440 (2004) and Phys. Rev. Lett. **92**, 259701 (2004).
- [5] V.M.Krasnov et al., Phys. Rev. Lett. **94**, 077003 (2005).